

## SYNTHESIS OF $Al_2O_3$ -Ni COMPOSITE POWDERS BY CO-PRECIPITATION METHOD

N. Maskani, R. Naghizadeh\* and A. Mirhabibi

\* rnaghizadeh@iust.ac.ir

Received: August 2016

Accepted: March 2017

School of Metallurgy and Materials Engineering, Iran University of Science and Technology, Tehran, Iran.

**Abstract:** The synthesis of micro-sized, uniformly distributed  $Al_2O_3$ -15Vol% Ni powders were studied through three step co-precipitation of hydroxides mixtures from proper solution, calcination at air atmosphere and final step of calcined powders in a carbon bed. Al and Ni hydroxide and amorphous phase were first obtained from their salt's solutions through chemical co-precipitation method by adjusting pH. The precipitated powders were then calcined to obtain a mixture of their oxides as NiO and  $NiAl_2O_4$  which were reduced in a carbon bed at various temperatures up to 1300°C. Proper temperature for calcination in air was determined through TG analysis; 900°C. SEM observation of powders after reduction, revealed micro-sized Ni particles, along with fin distribution of Ni and  $Al_2O_3$  elements. XRD analysis of the calcined sample showed the presence of  $NiAl_2O_4$  and NiO and the same analysis for the reduced sample confirmed the formation of  $Al_2O_3$  and Ni.

**Keywords:** Composite,  $Al_2O_3$ -Ni, Carbon Bed, Carbon Bed, Co-Precipitation,  $NiAl_2O_4$

### 1. INTRODUCTION

Alumina is a widely used ceramics for structural applications because it has high mechanical properties, thermal stability and corrosion resistant properties[1]. However, alumina ceramics are brittle with regard to fracture toughness. It well recognized that the fracture toughness of brittle ceramic materials can be increased by the addition of a dispersed second phase such as a ductile metal[2, 3]. The metallic phase can be either continuous or in the form of particulates homogeneously dispersed in the ceramic matrix. Furthermore, a microstructure with a highly-interconnected ceramic and metal network might offer some unique characteristics, since the continuous metal and ceramic phase could lead to improved fracture toughness and creep resistance respectively. Typically, ceramic-metal composites have been produced by dry mixing of ceramic and metal powders followed by hot pressing or sintering. This process is often difficult to control resulting in non-uniform dispersion of the components. In contrast, chemical techniques offer several advantages compared with traditional powder processing techniques such as greater control over

stoichiometry and microstructure. In addition, some chemical techniques have the advantage of simplicity and low cost, and they can be readily scaled up[4]. Although a small-scale homogeneity can be obtained using the sol-gel rout, the relatively high cost of some reactants and the difficulty to control the gel-drying step are drawbacks of the method[5]. The results of some studies, have demonstrated that the heterogeneous precipitation method is able to overcome difficulties in the second phase dispersion in matrix. Based on this method, two different salts precursors are utilized to produce the hydroxide or other composition of cation [6]. The literature on  $Al_2O_3$ -Ni composites prepared by the chemical method are few, so the present study aimed at synthesizing  $Al_2O_3$ -20vol%Ni submicron powders by chemical rout and produce a homogeneously dispersed powder with a narrow size range. Understanding and optimizing the precipitation process to achieve this was objective of the study as little is known for the  $Al_2O_3$ -Ni system in that regard.

### 2. EXPERIMENTAL

The precursor of  $Al_2O_3$  and Ni were aqueous solutions which were prepared by separately


dissolving 33.15 gr of  $\text{Al}(\text{NO}_3)_3 \cdot 3\text{H}_2\text{O}$  (99.0% purity, china) and 12.92 gr of  $\text{NiSO}_4 \cdot 6\text{H}_2\text{O}$  (99.0% purity, china) salts in the 150 ml and 125 ml distilled water, respectively. Concentration of Al and Ni ions was based on the stoichiometric proportions to produce a final  $\text{Al}_2\text{O}_3$ -20vol%Ni powder. The two precursor solutions were then mixed together and heated on a stirrer hot plate at  $60^\circ\text{C}$ . To adjust the pH to 8.8, ammonia solution was drop wised added and stirred for 2 h, in order to have desirable precipitated. The precipitate was separated by filtering and the remained solution was analyzed by ICP-OES determine any residual reactant elements. The precipitants were rinsed with water for several times and then dried at  $110^\circ\text{C}$  for 24 h. qualitative information about the different stretching and bending bonds at co-precipitation powders was studied with Fourier transformed infra-red spectrometry (FTIR, model Perkin Elmen) In order to determine the appropriate calcination temperature, the dried sample was subjected to thermogravimetry analysis (TG) up to  $1200^\circ\text{C}$  with a heating rate of  $10^\circ\text{C}/\text{min}$ (model D-32609 Hullhorst). Then the dried sample was calcined in an electrical muffle furnace at  $900^\circ\text{C}$  for 4 h in air to obtain oxide powders. The temperature for complete reduction of oxide phases in a carbon bed was determined by heating samples at various temperature ranges from  $1000^\circ\text{C}$  up to  $1300^\circ\text{C}$  at the rate of  $10^\circ\text{C}/\text{min}$  in a carbon bed. The products were analyzed by XRD (Siemens-Germany,Cu-K $\alpha$ ) to identify the present phases. The microstructure and morphology of the reduced powder and also their homogeneity were studied by scanning electron microscope (VEGA TESCAN Environmental SEM). Al and Ni distribution of material in different stages were investigated by elemental mapping using Energy-dispersive spectroscopy (EDS, model EPMH-8705Q\_Hz).

### 3. RESULTS AND DISCUSSION



#### 3. 1. Precipitation

The color of the precursor salts of Al and Ni were white and green, respectively. The nickel salt  $\text{NiSO}_4 \cdot 6\text{H}_2\text{O}$  is dissolved in water by ionizing



to  $\text{Ni}^{2+}$  and  $\text{SO}_4^{2-}$  resulting in an acidic solution. The aluminum salt  $\text{Al}(\text{NO}_3)_3 \cdot 3\text{H}_2\text{O}$  is dissolved in water by ionizing to  $\text{Al}^{3+}$  and  $\text{NO}_3^{-}$ , according to reactions.



After ionizing reactions, hydrolysis reactions have been occurred due to the following reactions[7, 8];



In second step, ammonia was added to the mixture solution to change the pH of the environment. The dissolution of ammonia in water produce  $\text{OH}^{-}$  and  $\text{NH}_4^{+}$  ions. In this case, Al precipitate as  $\text{Al}(\text{OH})_3$  and Ni precipitate as  $\text{Ni}(\text{OH})_2$  and  $\text{NiOOH}$ . The pH of the solution after adding adequate ammonia was about 8.8 and the color of the precipitates were light green. Equations (5-11) represent the suggested reactions[9-11]:



The residual Ni and Al in the remained solution after filtering the precipitate was analyzed by ICP which showed 1.2 and 0.85 ppm respectively. By these results it can be concluded that the chemical co-precipitation method has been successful in extracting Ni and Al from their solutions when pH is about 8.8. The XRD pattern of the precipitants is illustrated in Fig. 1. The

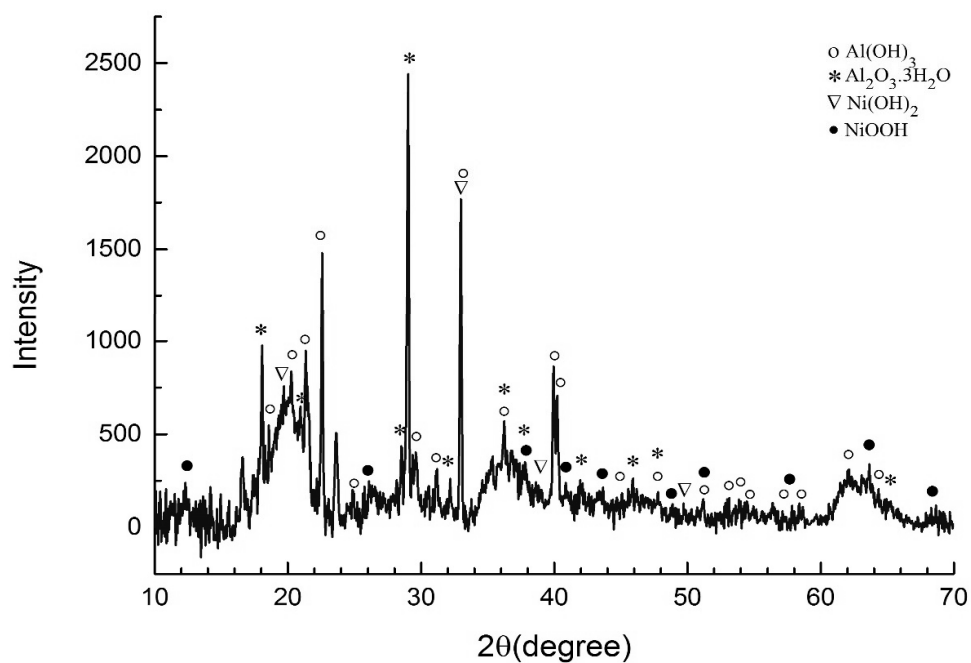


Fig. 1. XRD pattern of precipitated powders after drying at 110°C.

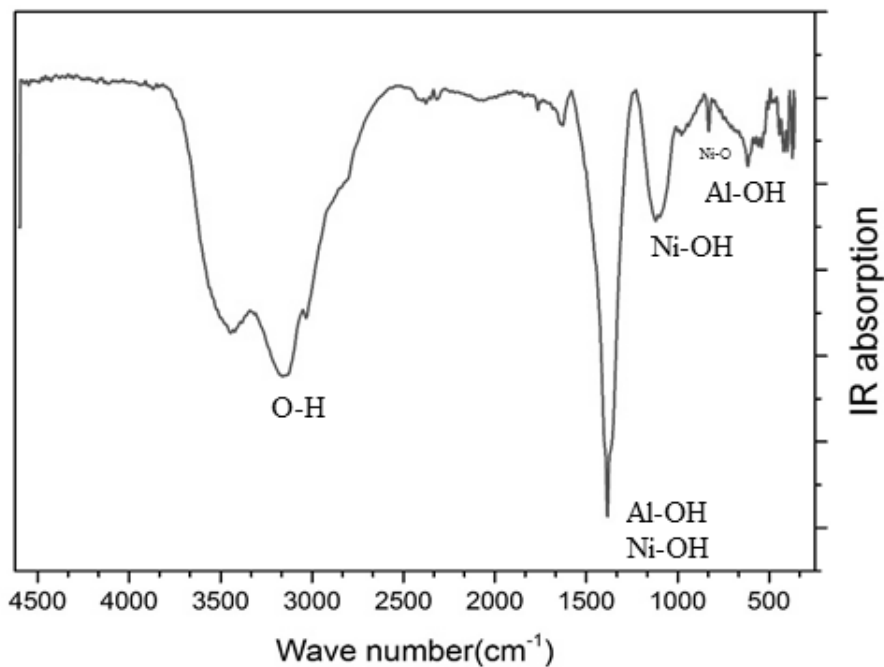


Fig. 2. The FTIR spectra of precipitated powders after drying at 110°C.

precipitates consist of nickel and aluminum hydroxides including:  $\text{Ni}(\text{OH})_2$ ,  $\text{NiOOH}$ ,  $\text{Al}(\text{OH})_3$  and with high amount of amorphous phase, as shown in background of XRD peaks. The FTIR profile of dried sample illustrated in Fig. 2, includes some absorption peaks related to the bonds between O, H, Ni and Al as hydroxide and oxide compounds. Detailed study on the bonds showed that there is a strong wide and deep absorption band in  $2800\text{-}3700\text{ cm}^{-1}$  that can be attributed to aqua (O-H-O) bending. This peak could be an indication of  $\text{Ni}(\text{OH})_2$  as well. The bonds around  $390\text{ cm}^{-1}$  is assigned to Ni-O stretching vibration mode.[12]

### 3. 2. Calcination

The thermogravimetric analysis of the dried samples performed between  $20^\circ\text{C}$  -  $1200^\circ\text{C}$  in air. Fig. 3 illustrates the TG curve of the dried precipitated powder. The TG curve presents two well defined mass loss steps which culminate at  $220\text{-}450^\circ\text{C}$  and  $750\text{-}900^\circ\text{C}$ . The first 52% mass

loss corresponds to decomposition of Al and Ni hydroxides. Generally  $\text{Ni}(\text{OH})_2$  and  $\text{Al}(\text{OH})_3$  are converted to  $\text{NiO}$  and transition form of  $\text{Al}_2\text{O}_3$  at  $350^\circ\text{C}$  and  $300\text{-}500^\circ\text{C}$  respectively[1,15]. The second 15% mass loss corresponds to transition of aluminum transition form to drier form and removal of OH and probably residual sulfate composition. There are 34% OH phase In transition alumina that exit from structure above  $500^\circ\text{C}$  [13]. As it can be seen any appreciable weight loss when the sample was heated above  $900^\circ\text{C}$  and it was considered as calcination temperature.

Fig. 4 shows the XRD pattern of the powder after calcination at  $900^\circ\text{C}$  in air atmosphere for 4 h.  $\text{NiO}$  and  $\text{NiAl}_2\text{O}_4$  peaks are clearly observed. Reaction of  $\text{NiO}$  and  $\text{Al}_2\text{O}_3$  begin between  $700\text{-}900^\circ\text{C}$  according to particle size and activity of raw material[17]. Duo to solubility of  $\text{Al}_2\text{O}_3$  in  $\text{NiAl}_2\text{O}_4$ , excess  $\text{Al}_2\text{O}_3$  were not observed at calcined powders[7,12].

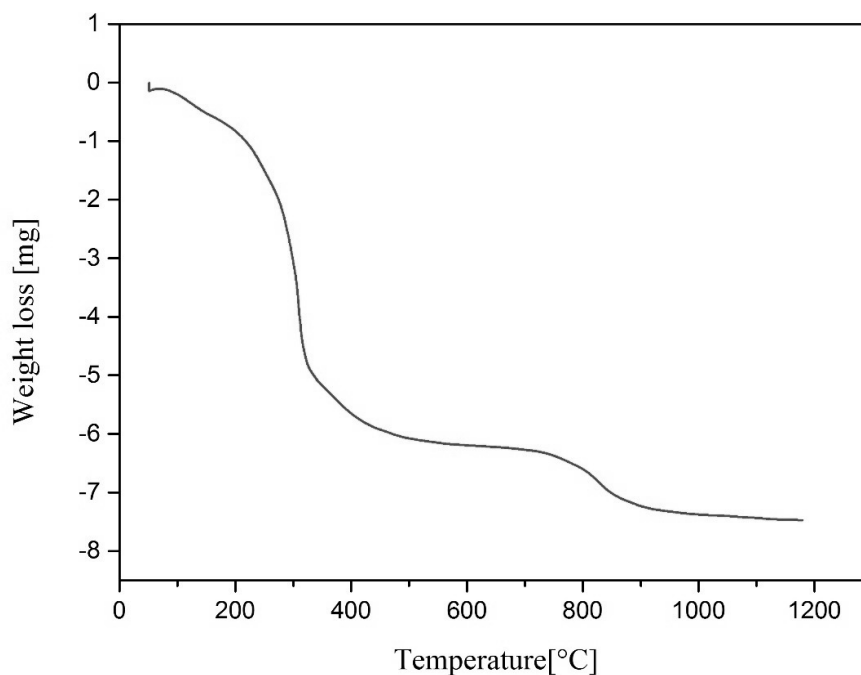


Fig. 3. The TG curve of dried sampel with the rate of  $10^\circ\text{C}/\text{min}$  in air.

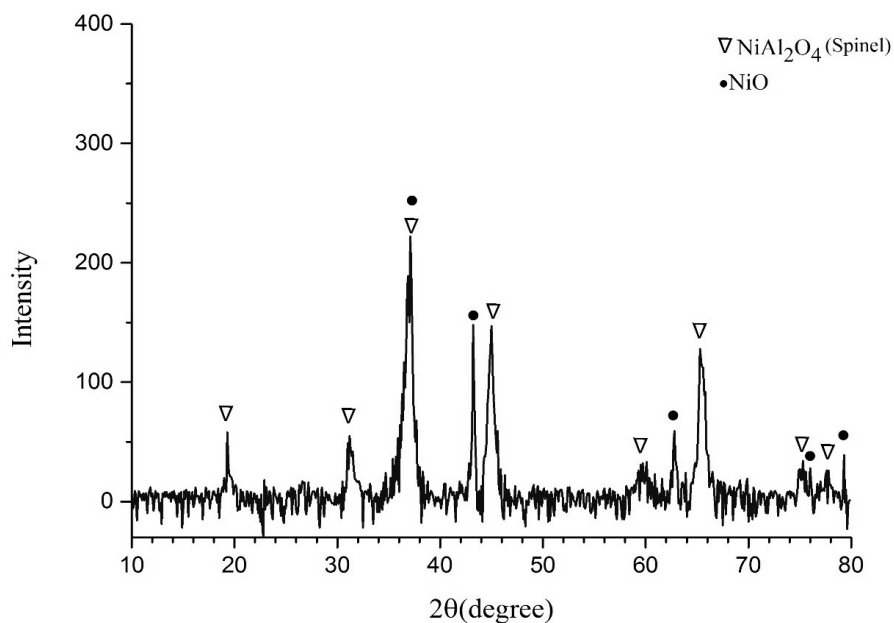


Fig. 4. The XRD pattern precipitated powders after calcination at 900 °C for 4h in air atmosphere.

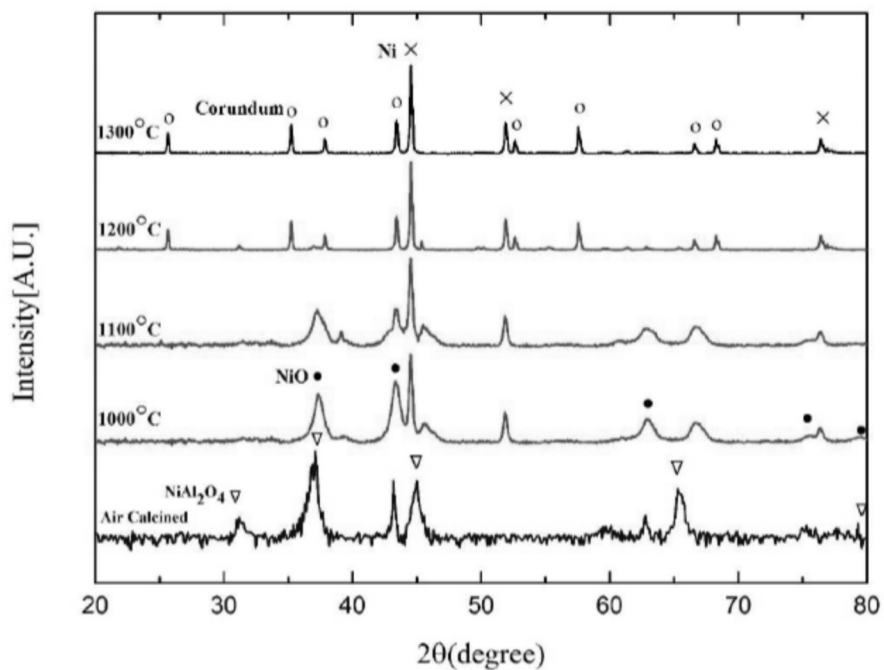
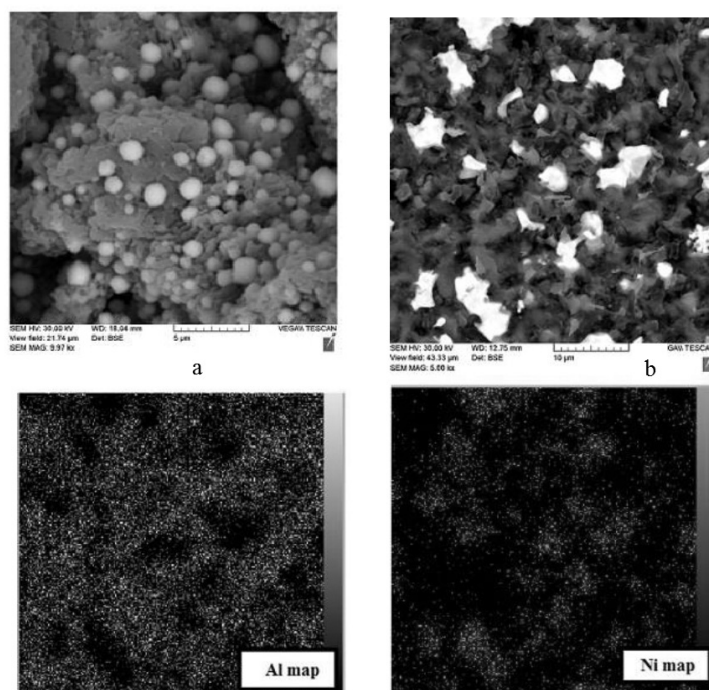


Fig. 5. The XRD pattern of calcined powders after reduction in carbon bed at different temperature for 3h.



**Fig. 6.** The SEM micrograph of the two reduced samples at a) at 1300 for 3h, b) at 1650 for 2h, c) corresponding Map of micrograph b

### 3. 3. Reduction

The XRD pattern of calcined powder heated in a carbon bed at various temperature are shown in Fig. 5. As reported by Toshihiro Isob, decomposition of  $\text{NiAl}_2\text{O}_4$  and formation of NiO and  $\text{Al}_2\text{O}_3$  occur above  $700^\circ\text{C}$  in reduction atmosphere and this NiO was reduced to Ni metal above  $800^\circ\text{C}$  [14].  $\text{Al}_2\text{O}_3$  which was formed by decomposition of spinel was transformed to  $\alpha\text{-Al}_2\text{O}_3$  at  $\geq 1300^\circ\text{C}$ , and the obtained sample is consisted of  $\alpha\text{-Al}_2\text{O}_3$  and Ni [19].

Fig. 6 shows the SEM micrograph of reduced sample in two different temperature. It appears from elemental map that Ni particles are bright and  $\text{Al}_2\text{O}_3$  particles are gray ones. SEM images shows uniform distributed Ni particles.

### 4. CONCLUSION

Aluminum and nickel hydroxides such as  $\text{Al}(\text{OH})_3$ ,  $\text{Ni}(\text{OH})_2$ ,  $\text{NiOOH}$ , and amorphous

phases were coprecipitated from solution of aluminum nitrate and nickel sulfate at  $60^\circ\text{C}$  and pH 8.8. A mechanism for the formation of the precipitates was deduced based on the characterization of precipitates. After calcination of dried precipitated powders at  $900^\circ\text{C}$  for 4 hours  $\text{NiAl}_2\text{O}_4$  spinel and NiO were obtained. After reduction of calcined powders composite powders at  $1300^\circ\text{C}$  for 3 hours, alumina nickel composite was obtained that showed uniformly dispersed micro-sized nickel in alumina matrix.

### REFERENCES

1. Gitzen, W. H., "Alumina as a ceramic material, .wiley " 1970.
2. Ding, J., Liu, B. H., Dong, Z. L., Zhong, Z., Lin, J., and White, T., "The preparation of  $\text{Al}_2\text{O}_3/\text{M}$  (Fe, Co, Ni) nanocomposites by mechanical alloying and the catalytic growth of carbon nanotubes," Composites Part B: Engineering, 2004, vol. 35, pp. 103-109,

3. Portu, G. de, Guicciardi, S., Melandri, C., and Monteverde, F., "Wear behaviour of  $\text{Al}_2\text{O}_3$ -Mo and  $\text{Al}_2\text{O}_3$ -Nb composites," *Wear*, 2007, vol. 262, pp. 1346-1352,
4. Rodeghiero, E., Tse, O., Chisaki, J., and Giannelis, E., "Synthesis and properties of Ni- $\alpha$ - $\text{Al}_2\text{O}_3$  composites via sol-gel," *Materials Science and Engineering: A*, 1995, vol. 195, 151-161,.
5. Li, G. J., Huang, X. X., and Guo, J. K., "Fabrication, microstructure and mechanical properties of  $\text{Al}_2\text{O}_3$ /Ni nanocomposites by a chemical method," *Materials research bulletin*, 2003, vol. 38, 1591-1600.
6. Li, G. j., Huang, X. X., and Guo, J. k., "Fabrication of Ni-coated  $\text{Al}_2\text{O}_3$  powders by the heterogeneous precipitation method," *Materials research bulletin*, 2001, vol. 36, 1307-1315.
7. Wefers, K., and Misra, C., "Oxides and hydroxides of aluminum, Alcoa Research Laboratories " 1987.
8. Zubryckyj, N., Kunda, W., and Evans, D., "Extra-High-Purity Nickel Powder from Nickel Sulfate Solution by Hydrogen Reduction," *Journal of The Electrochemical Society*, 1969, vol. 116, 542-546.
9. Huang, J. J., Hwang, W. S., Weng, Y. C., and Chou, T. C., "Transformation Characterization of Ni (OH)<sub>2</sub>/NiOOH in Ni-Pt Films Using an Electrochemical Quartz Crystal Microbalance for Ethanol Sensors," *Materials transactions*, 2010, vol. 51, 2294-2303.
10. Ramesh T. and Kamath P. V., "Synthesis of nickel hydroxide: effect of precipitation conditions on phase selectivity and structural disorder," *Journal of power sources*, 2006 vol. 156, 655-661.
11. Hek, H. De, Stol, R., and Bruyn, P. De, "Hydrolysis-precipitation studies of aluminum(III) solutions. 3. The role of the sulfate ion," *Journal of Colloid and Interface Science*, 1978, vol. 64, 72-89.
12. Jeevanandam P., Koltypin Y., and Gedanken A., "Preparation of nanosized nickel aluminate spinel by a sonochemical method," *Mater. Sci. Eng. B*, 2002, vol. 90, 125-132.
13. Strekopytov, S. and Exley, C., "Thermal analyses of aluminium hydroxide and hydroxyaluminosilicates," *Polyhedron*, 2006, vol. 25, 1707-1713.
14. Cui, H., Zayat, M., and Levy, D., "A sol-gel route using propylene oxide as a gelation agent to synthesize spherical  $\text{NiAl}_2\text{O}_4$  nanoparticles," *Journal of non-crystalline solids*, 2005, vol. 351, 2102-2106.
15. Li, G., Huang X., and Guo J., "Fabrication and mechanical properties of  $\text{Al}_2\text{O}_3$ -Ni composite from two different powder mixtures," *Mater. Sci. Eng. A*, 2003, vol. 352, 23-28.
16. LeRoy, L. D., Hart, D. and Lense, E., "Alumina chemicals : science and technology handbook. American Ceramic Society, 1990, wiley.
17. Rotan, M., Tolchard, J., Rytter, E., Einarsrud, M. A., and Grande, T. "On the solid solution of the spinel phase in the system NiO- $\text{Al}_2\text{O}_3$ ," *J. Solid State Chem*, 2009, vol. 182, 3412-3415.
18. Rotgerink, H. G. J. L., Bosch, H., Van Ommen, J. G., and Ross, J. R. H., "The effect of Ni-Al ratio on the properties of coprecipitated nickel-alumina catalysts with high nickel contents, 1986," *Appl. Catal.*, vol. 27, 41-53.
19. Üstündag, E., Subramanian, R., Dieckmann, R., and Sass, S. L., "In situ formation of metal-ceramic microstructures in the Ni-Al-O system by partial reduction reactions," *Acta Metall. Mater.*, Jan. 1995, vol. 43, no. 1. 383-389.